

Lloyd's Register of Shipping.

er: 328

ks No: 35566/Pr.

chstr. 9258

t: 1469

Surveyors' Office, VIENNA.


No: 2 7 5 3

4 3 3 9

to certify, that **Heinrich Schneider** the undersigned surveyor to this Society tested in
 works of **Messrs. Witkowitz Bergbau & Eisenhütten Gew.** of **Witkowitz**
annealed Siemens Martin Boiler steel **plates** specified hereunder, ordered
Messrs. Cantieri Navali ed Acciaierie di Venezia of **Venezia**
S.A.
 e ship No. **74** Boiler No. **56/57** and that the results of tests were as are set forth below.

Dimensions. in millimeters			Intended for	Sample number	Charge- number	Tensile tenacity in Kg/mm ²			Elongation in 200 mm. in %.	Bending tests.		LLOYDS 4339 Remarks. HS.3.12. 1930	S
Length.	Breadth.	Thick- ness.				As per rules.	Ord- ered.	By test.		Cold.	Tem- pered		
900	outs.	22	front end pl.	370	9307	41	41	45.6	25	g	o	No: 720	5/6
"	"	"	" " "	C	"	47	47	42.4	24	"	"	No: 721	7
"	"	"	" " "	373	"	"	"	43.1	27	"	"	No: 722	8
"	"	"	back " "	C	"	"	"	45.9	26	"	"	No: 723	
"	"	"	" " "	371	"	"	"	45.6	24	"	"	No: 724-	
"	"	"	" " "	C	"	"	"	42.4	29	"	"	27	
"	"	"	" " "	372	"	"	"	45.7	29	"	"	No: 728-	
"	"	"	" " "	C	"	"	"	42.6	29	"	"	30	
"	"	18	press.front pl. right & left	374	9296	"	"	46.4	24	"	"	No: 731	
"	"	16	press.back pl right & left	375	9307	"	"	42.6	27	"	"	No: 732-	
"	"	"	" " "	376	9340	"	"	44.7	26	"	"	33	
"	"	18	press.front centre pl.	377	9307	"	"	44.9	27	"	"	No: 734-	
"	"	16	press.back centre pl.	378	"	"	"	42.6	28	"	"	35	
200	72	20	Dom end pl. with manhole	379	9296	"	"	44.4	25	"	"	No: 736-	
400/300	18	manhole covers	380	9307	"	"	"	42.6	26	"	"	37	
"	"	6	manhole dogs	381	9296	"	"	44.1	29	"	"	No: 738-	
"	"					"	"			"	"	43	
"	"					"	"			"	"	No: 744	

V i e n n a, 13th December 1930

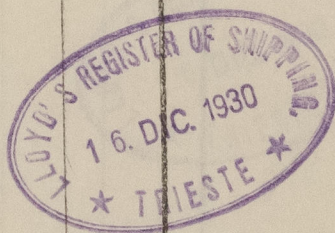

Heinrich Schneider
 SURVEYOR TO LLOYDS REGISTER

This Certificate is issued upon the terms of the Rules and Regulations of the Society, which provide that:—

"While the Committee use their best endeavours to ensure that the functions of the Society are properly executed, it is to be understood that neither the Committee nor the Society are under any circumstances whatever to be held responsible for any inaccuracy in any report or certificate issued by the Society or its Surveyors, or in any entry in the Register Book or other publication of the Society, or for any error of judgment, default, or negligence of the Surveyors, or other Officers or Agents of the Society."

N.B.—Material with less than 26 Tons tensile strength may not be used in the construction of boilers for classed vessels, unless specially sanctioned by the Committee.

1 Ton per square inch = 1,574 Kilo per square millimeter. 1 Kilo per square millimeter = 0,635-Tons per square inch.

005118-005131-0287