


Reinforced concrete Warge.
 Yard No. 2. P.D. No. 92.
 Test "B" Mixture No. 1.

1st May. 1919

three four-inch cubes of concrete, received from yourselves

NO.	DESCRIPTION	WEIGHT	DIMENSIONS	AGE	CRUSHING STRENGTH		
					TOTAL	PER SQ. INCH	PER SQ. FOOT
BBB	Age 7 days.						
2062	^{cubes marked} M4 J.M.G. 5.41 4.00 3 7/8 x 4.00 15.54 24/9/19	5.41	4.00 3 7/8 x 4.00	15.54	29,800	1880	120.9
2063	Proportions 1 part cement (Albert How & Rhoads) 115 parts sand (Loch Ridden) 2.30 parts aggregate (2 parts Shirlfield Granite) (1 part Dalbeattie Granite)	5.53	4.04 4.00 x 4.04 16.16	16.16	29,800	1840, 1890	118.3, 121.7
2064	do.	5.48	4.00 4.00 x 4.04 16.16	16.16	31,700	1960	126.0

Messrs The Scottish Concrete Ship Co. Ltd.
 Battery Park, Greenock.

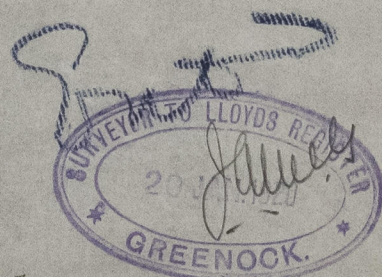

David H. H. H.



© 2021

Lloyd's Register
 Foundation